



UDC 669.52

DOI: 10.31643/2020/6445.31



IRSTI 53.37.91, 31.15.33

## Study of leaching processes of sintered black shale ore

\* **Khabiyev A. T., Baigenzhenov O. S., Yulussov S. B., Akbarov M. S., Sydykanov M. M.**

*Satbayev University, Almaty, Kazakhstan*

\* *Corresponding author email: alibek1324@mail.ru, a.khabiyev@satbayev.university*

### ABSTRACT

This paper presents the results of physical and chemical investigation of black shale ore, as well as the investigation of combination of hydro- and pyrometallurgical methods in the sintering process of black shale ore with ammonium hydrosulfate to convert metals into water-soluble form. The homogeneous composite of black shale ore taken for the study consists of 67 % SiO<sub>2</sub>, 18 % C and 3 % H<sub>2</sub>O, 0.683 % V, 0.0415 Mo, 0.0148 % U<sub>3</sub>O<sub>8</sub> and other components. Thermogravimetric analysis of sintering of carbon-silica ore with ammonium hydrosulfate in the presence of sulfuric acid was performed in the temperature range 20-1000 °C. It is established that at low-temperature sintering of ore with hydrosulfate ammonium after further leaching with sulfuric acid solution the extraction of uranium, vanadium, molybdenum and rare earth metals is 98.2 %, 91.3 %, 82.2% and 78.3 % respectively. The optimal leaching temperature is 90 °C, the ratio S: L = 1:3, and the leaching time is 2 hours.

**Keywords:** black shale ore, sintering, leaching, uranium, vanadium, molybdenum, rare earth elements

*Received: 10 September 2020  
Peer-reviewed: 22 September 2020  
Accepted: 13 October 2020*

### Information about authors:

**Khabiyev Alibek Talgatbekovich**

*Doctor Ph.D., Assoc. Professor. Non-commercial joint-stock company "Satbayev University", the department "Metallurgical processes, heat engineering and technology of special materials", Almaty, the Republic of Kazakhstan, <https://orcid.org/0000-0001-9397-2367>. E-mail: a.khabiyev@satbayev.university*

**Baigenzhenov Omirserik Sabyrzhanovich**

*Doctor Ph.D., Assoc. Professor. Non-commercial joint-stock company "Satbayev University", the department "Metallurgical processes, heat engineering and technology of special materials", Almaty, the Republic of Kazakhstan <https://orcid.org/0000-0001-5803-7680>. E-mail: o.baigenzhenov@satbayev.university*

**Yulussov Sultan Baltabaevich**

*Ph.D. student. Non-commercial joint-stock company "Satbayev University", the department "Metallurgical processes, heat engineering and technology of special materials", Almaty, the Republic of Kazakhstan, <https://orcid.org/0000-0001-8044-4186>, E-mail: s1981b@mail.ru*

**Akbarov Merey Sabitovich**

*Lector, Non-commercial joint-stock company "Satbayev University", Almaty, Kazakhstan. <https://orcid.org/0000-0002-4272-8038>, E-mail: akbarov\_meron@mail.ru*

**Sidikanov Muratbek Mukhtarbekovich**

*Ph.D. student. Non-commercial joint-stock company "Satbayev University", the department "Metallurgical processes, heat engineering and technology of special materials", Almaty, the Republic of Kazakhstan, <https://orcid.org/0000-0002-9988-6440>. E-mail: mura\_kaz@mail.ru*

## Күйдірілген қара сланецтік кендерді шаймалау процестерін зерттеу

\* **Хабиев А.Т., Байгенженов О.С., Юлусов С.Б., Акбаров М.С., Сыдыканов М.М.**

*Сатбаев университеті, Алматы, Қазақстан*

\* *Корреспондент автордың электрондық почтасы: alibek1324@mail.ru, a.khabiyev@satbayev.university*

### ТҮЙІНДЕМЕ

Бұл жұмыста көміртегі-кремний кенін физика-химиялық зерттеу нәтижелері, сондай-ақ металдарды суда еритін формаға айналдыру үшін көміртегі-кремний кенін аммоний гидросульфатымен біріктіру процесін зерттеу нәтижелері келтірілген. Зерттеу үшін алынған қара тақтатаст кенінің біртекті композиті 67% SiO<sub>2</sub>, 18% C және 3% H<sub>2</sub>O, 0,683% V, 0,0415 Mo, 0,0148% U<sub>3</sub>O<sub>8</sub> және басқа компоненттерден тұрады. Күкірт қышқылының қатысуымен аммоний гидросульфаты бар көміртегі-кремнийлі кенді синтездеуге термогравиметриялық талдау 20 – 1000 °C температура аралығында жүргізілді. Аммоний гидросульфатымен кенді төмен температурада жентектеу кезінде күкірт қышқылы ерітіндісімен одан әрі шаймалаудан кейін уран, ванадий, молибден және сирек жер металдарын алу тиісінше 98,2 %, 91,3 %, 82,2 % және

*Мақала келді: 10 қыркүйек 2020  
Рецензенттен өтті: 22 қыркүйек 2020  
Қабылданды: 13 қазан 2020*

78,3 % құрайтыны анықталды. Бұл жағдайда шаймалаудың оңтайлы температурасы 90 °С, қатынасы Қ:С = 1:3 және шаймалау уақыты-2 сағат.

**Түйін сөздер:** көміртек-кремнийлі кендер, күйдіру, шаймалау, уран, ванадий, молибден, сирек жер элементтері.

<b>Хабиев Әлібек Талғатбекулы</b>	<b>Авторлар туралы ақпарат:</b> Ph.D докторы, доцент-профессор, Сәтбаев университеті, «Металлургиялық процестер, жылу техникасы және арнайы материалдар технологиясы» кафедрасы, Алматы қ., Қазақстан Республикасы. ORCID ID: <a href="https://orcid.org/0000-0001-9397-2367">https://orcid.org/0000-0001-9397-2367</a> . Электрондық пошта: <a href="mailto:a.khabiyev@satbayev.university">a.khabiyev@satbayev.university</a>
<b>Байгенженов Өмірсерік Сабыржанұлы</b>	Ph.D докторы, доц. профессор. Сәтбаев университеті, «Металлургиялық процестер, жылу техникасы және арнайы материалдар технологиясы» кафедрасы, Алматы қ., Қазақстан Республикасы. ORCID ID: <a href="https://orcid.org/0000-0001-5803-7680">https://orcid.org/0000-0001-5803-7680</a> . Электрондық пошта: <a href="mailto:o.baigenzhenov@satbayev.university">o.baigenzhenov@satbayev.university</a>
<b>Юлусов Сұлтан Балтабайұлы</b>	PhD студент, Сәтбаев университеті, «Металлургиялық процестер, жылу техникасы және арнайы материалдар технологиясы» кафедрасы, Алматы қ., Қазақстан Республикасы. ORCID ID: <a href="https://orcid.org/0000-0001-8044-4186">https://orcid.org/0000-0001-8044-4186</a> , Электрондық пошта: <a href="mailto:s1981b@mail.ru">s1981b@mail.ru</a>
<b>Ақбаров Мерей Сәбитұлы</b>	Лектор, Сәтбаев университеті, Алматы қ., Қазақстан Республикасы. ORCID ID: <a href="https://orcid.org/0000-0002-4272-8038">https://orcid.org/0000-0002-4272-8038</a> , Электрондық пошта: <a href="mailto:akbarov_meron@mail.ru">akbarov_meron@mail.ru</a>
<b>Сидиқанов Мұратбек Мұхтарбекулы</b>	PhD студент, Сәтбаев университеті, «Металлургиялық процестер, жылу техникасы және арнайы материалдар технологиясы» кафедрасы, Алматы қ., Қазақстан Республикасы. ORCID ID: <a href="https://orcid.org/0000-0002-9988-6440">https://orcid.org/0000-0002-9988-6440</a> . Электрондық пошта: <a href="mailto:mura_kaz@mail.ru">mura_kaz@mail.ru</a>

## Исследование процесса выщелачивания обожженной черносланцевой руды

\* Хабиев А.Т., Байгенженов О.С., Юлусов С.Б., Ақбаров М.С., Сыдықанов М.М.

Satbayev University, Алматы, Казахстан

\* Электронная почта корреспондента автора: [alibek1324@mail.ru](mailto:alibek1324@mail.ru), [a.khabiyev@satbayev.university](mailto:a.khabiyev@satbayev.university)

Статья поступила: 10 сентября 2020 Рецензирование: 22 сентября 2020 Принята в печать: 13 октября 2020	<b>АННОТАЦИЯ</b> В данной работе представлены результаты физико-химических исследований углерод-кремнеземистой руды Большого Каратау, а также исследования процесса спекания углерод-кремнеземистой руды с гидросульфатом аммония для превращения металлов в водорастворимую форму. Гомогенный композит черной сланцевой руды, взятый для исследования, состоит из 67 % SiO <sub>2</sub> , 18 % С и 3 % Н <sub>2</sub> O, 0,683 % V, 0,0415 Мо, 0,0148 % U <sub>3</sub> O <sub>8</sub> и другие компоненты. Термогравиметрический анализ спекания углерод-кремнеземистой руды с гидросульфатом аммония в присутствии серной кислоты проводили в интервале температур 20 – 1000 °С. Установлено, что при низкотемпературном спекании руды с гидросульфатом аммония после дальнейшего выщелачивания раствором серной кислоты извлечение урана, ванадия, молибдена и редкоземельных металлов составляет 98,2 %, 91,3 %, 82,2 % и 78,3 % соответственно. При этом оптимальная температура выщелачивания составляет 90 °С, соотношение Т: Ж = 1:3 и время выщелачивания-2 часа. <b>Ключевые слова:</b> черносланцевые руды, спекание, выщелачивание, уран, ванадий, молибден, редкоземельные элементы.
<b>Хабиев Алибек Талғатбекович</b>	<b>Информация об авторах:</b> Ph.D., доц. профессор. Некоммерческое акционерное общество «Satbayev University», кафедра «Металлургические процессы, теплотехника и технология специальных материалов», г. Алматы, Республика Казахстан. ORCID ID: <a href="https://orcid.org/0000-0001-9397-2367">https://orcid.org/0000-0001-9397-2367</a> . E-mail: <a href="mailto:a.khabiyev@satbayev.university">a.khabiyev@satbayev.university</a>
<b>Байгенженов Омирсерік Сабыржанович</b>	Ph.D., доц. профессор. Некоммерческое акционерное общество «Satbayev University», кафедра «Металлургические процессы, теплотехника и технология специальных материалов», г. Алматы, Республика Казахстан. ORCID ID: <a href="https://orcid.org/0000-0001-5803-7680">https://orcid.org/0000-0001-5803-7680</a> . E-mail: <a href="mailto:o.baigenzhenov@satbayev.university">o.baigenzhenov@satbayev.university</a>
<b>Юлусов Султан Балтабаевич</b>	Ph.D студент. Некоммерческое акционерное общество «Satbayev University», кафедра «Металлургические процессы, теплотехника и технология специальных материалов», г. Алматы, Республика Казахстан. ORCID ID: <a href="https://orcid.org/0000-0001-8044-4186">https://orcid.org/0000-0001-8044-4186</a> , E-mail: <a href="mailto:s1981b@mail.ru">s1981b@mail.ru</a>
<b>Ақбаров Мерей Сабитович</b>	Лектор, Некоммерческое акционерное общество «Satbayev University», г. Алматы, Республика Казахстан. ORCID ID: <a href="https://orcid.org/0000-0002-4272-8038">https://orcid.org/0000-0002-4272-8038</a> , E-mail: <a href="mailto:akbarov_meron@mail.ru">akbarov_meron@mail.ru</a>
<b>Сидиқанов Мұратбек Мұхтарбекович</b>	Ph.D студент. Некоммерческое акционерное общество «Satbayev University», кафедра «Металлургические процессы, теплотехника и технология специальных материалов», г. Алматы, Республика Казахстан. ORCID ID: <a href="https://orcid.org/0000-0002-9988-6440">https://orcid.org/0000-0002-9988-6440</a> . Электронная почта: <a href="mailto:mura_kaz@mail.ru">mura_kaz@mail.ru</a>

## Introduction

Recently, several new technologies with different advantages have been developed for the processing of black shale ores, including sulphation atmospheric leaching [1, 2], autoclave (pressure acid) leaching [3], leaching of roasted shales etc. [4]. Autoclave leaching is one of the common hydrometallurgical processes used to processing black shale ores on industrial scales. High pressure acid leaching and heap leaching processes offer some advantages in terms of the leaching processes. However, they also have several drawbacks, such as large capital expenditure for the construction of the leaching equipment, maintenance of the bed permeability under acidic leaching conditions, control of the acid consumption, inventory and cycle time management, and water management. Acid consumption in the pressure acid leaching process was less than in atmospheric leaching with iron precipitation as jarosite [5]. Low levels of sulphuric acid were used to extract of vanadium from black shale ores using the sulphation atmospheric leaching process, in conjunction with relatively low levels of recovery. Numerous processes have been developed on the commercial scale but have failed to get a satisfactory yield with the operating costs. As reported that [6], pregnant sulphuric acid leach solutions are more amenable to downstream processing by sorption and solvent extraction processes.

## Experimental part

**Materials.** The objects of the investigation were representative samples of black shale ore of the Big Karatau. They were crushed to a particle size of 0.2 mm. Chemical, X-ray phase, spectral and thermographic methods were used for analyzes of initial products.

In general, the ores of the Big Karatau have a diverse mineral composition. Black shale ore are of magmatic origin and are metamorphic rocks [7]. From the mineralogical and X-ray spectral analysis of black shale ore from the Balasauskandyk field of Big Karatau, South Kazakhstan region, performed on an electron-probe microanalyzer with the usage of an energy-dispersive spectrometer, it follows that all valuable ore minerals are in a siliceous carbon matrix.

The homogeneous composite of black shale ore consists of 67 % SiO<sub>2</sub>, 18 % C and 3 % H<sub>2</sub>O. They also include non-ferrous, rare, radioactive and rare earth

metals. The full composition of black shale ore from the Balasauskandyk deposit is revealed in Table 1.

**Thermogravimetric analysis of sintered black shale ores.** A thermogravimetric analysis to investigate black shale ore was carried out. It was determined a derivatogram of ore decomposition at various temperatures. Besides it was investigated a sintering of black shale ore with ammonium hydrosulfate.

During the sintering process at a temperature of 100-350 °C, water is removed by dehydration. According to the results of thermogravimetric method of analysis in the temperature range from 100 to 387 °C is the removal of water.

Data from DTA and thermogravimetric measurements of the system under study (Fig. 1, table. 2) clearly demonstrate changes in the quality and quantity of its components. During the release of H<sub>2</sub>O and CO<sub>2</sub> into the atmosphere, the analysis provides information about changes in the substance at the level of chemical compounds.

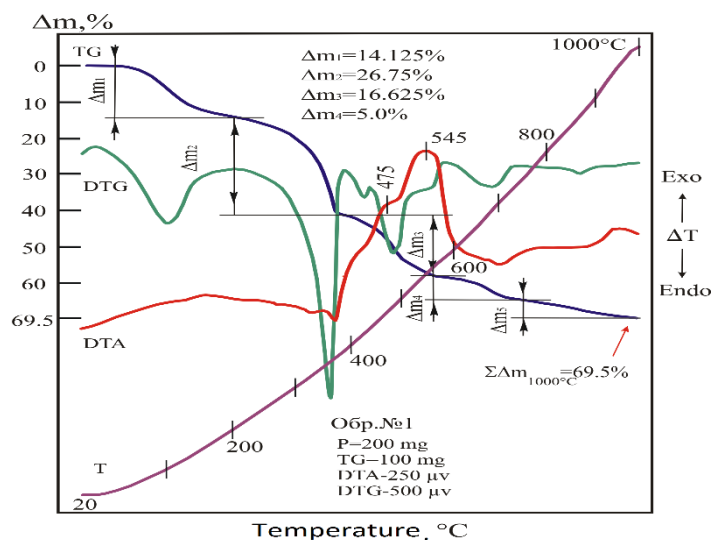
The first minimum on the curve of DTA, located at about 100 °C, can be attributed to the manifestation of the removal of adsorbed moisture sample. Also, in the development of this effect (after 100 °C), it is possible to release gases sorbed by coal, consisting mainly of nitrogen and carbon dioxide. The exothermic effect with a peak at 475 °C reflects the oxidation of coal. CO and CO<sub>2</sub> may be present in the gas phase. The endothermic effect with an extremum at 385 °C corresponds to the intense minimum on the DTA curve. This may be presumably a manifestation of gas discharge of the organic component of the sample. It is indicated that decarboxylation and dihydroxylation reactions are possible here, i.e. separation of the least stable carbonyl and hydroxyl groups.

Ammonium hydrosulphate melts at 149 °C. On closer examination of the DTA curve, a weak endothermic effect (weak bend) can be seen at approximately this temperature. At 490 °C ammonium hydrosulfate boils. Perhaps, at this temperature, its decomposition reaction with the formation of ammonia, SO<sub>3</sub> and water is feasible. It is possible that this reaction was the cause of the minimum on the curve of DTH at about 500 °C.

The exothermic effect on the DTA curve with a peak at 545 °C most likely reflects the oxidation of pyrite. The final oxidation product in this process is hematite. Herewith sulfur dioxide SO<sub>2</sub> enters the gas phase. The minimum on the DTG curve after 800 °C (on the DTA curve it corresponds to a weak endothermic inflection) can be a manifestation of

**Table 1** - Composition of black shale ore of the Balasauskandyk deposit

Element	Content, %	Element	Content, %	Element	Content, %
Al <sub>2</sub> O <sub>3</sub>	3,79	S	0,80	Ba	0,776
Fe <sub>2</sub> O <sub>3</sub>	2,07	Sr	0,049	V	0,683
K <sub>2</sub> O	1,16	C	18	Co	0,0082
CaO	0,383	Cr	0,042	Cu	0,0418
SiO <sub>2</sub>	72,35	WO <sub>3</sub>	0,0352	Mo	0,0415
MgO	0,29	Y <sub>2</sub> O <sub>3</sub>	0,0241	Nd <sub>2</sub> O <sub>3</sub>	0,0071
Na <sub>2</sub> O	0,0678	U <sub>3</sub> O <sub>8</sub>	0,0148	SeO <sub>2</sub>	0,0068
TiO <sub>2</sub>	0,119	ZrO <sub>2</sub>	0,0105	Tb <sub>4</sub> O <sub>7</sub>	0,0047
P <sub>2</sub> O <sub>5</sub>	1,15	CeO <sub>2</sub>	0,0095	Rb <sub>2</sub> O	0,0035

**Figure 1** - Derivatogram of decomposition of black shale ore under low heat sintering**Table 2** - Thermogravimetric indications of sintering in the range of 20-1000 °C

Sequence of weight loss	The amount of weight loss in %	Estimated emissions at appropriate stages of decomposition	Temperature ranges of decomposition stages, °C
$\Delta m_1$	14.125	H <sub>2</sub> O, CO <sub>2</sub>	20-385
$\Delta m_2$	26.75	C, H, N	385-570
$\Delta m_3$	16.625	C, H, N	570-650
$\Delta m_4$	197.0.0	CO <sub>2</sub> , H, N	650-735
$\Delta m_5$	5.0	CO <sub>2</sub> , H, N, SO <sub>2</sub>	735-1000
$\Sigma \Delta m_{1000^\circ C}$	80.5	H <sub>2</sub> O, C, H, N, NO <sub>2</sub> , CO <sub>2</sub> , SO <sub>2</sub> ,	20-1000

dehydration of muscovite or sericite. The combination of the endothermic effect with an extremum located near 700 °C and the above-mentioned minimum can be attributed to the decomposition of the carbonate ore - hantite CaMg<sub>3</sub>[CO<sub>3</sub>]<sub>4</sub>. Separately, the endothermic effect with an extremum located near 700 °C is a manifestation of the decomposition of calcite, accompanied by the release of carbon dioxide.

**Leaching studies of sintered black shale ores.** In this study, samples of black shale ores (100 g) were ground to a size of 0.2 mm, thoroughly mixed with ammonium hydrosulfate (NH<sub>4</sub>)HSO<sub>4</sub> in a ratio of 1:0.75 (75 g of ammonium hydrosulfate) and

sintered in a muffle electroheating furnace SNOL 40/1200 at 350 °C for 2 h. All leaching tests were carried out in a temperature-controlled three-necked flat bottom glass flask (cap. 250 mL) on hot-plate cum magnetic stirrer at fixed rpm (400) and a reflux condenser to avoid the loss due to evaporation. Leaching the applicability sulfuric acid leaching was studied. The leaching time was recorded after successive addition of the sintered black shale ores and sulphuric acid solution (10-60 g/L, S:L ratio = 1:3) to the reaction vessel, and then put this vessel in an oil bath maintained at a preset temperature 90 °C. The choice of leaching temperature is due to the fact that at low

**Table 3** - Results of leaching of sintered products with sulfuric acid

The concentration of sulfuric acid, g/L	Content of, g/L			
	V	U	Mo	REE
10	0,81	0,026	0,024	0,014
20	1,01	0,037	0,047	0,021
30	1,17	0,049	0,062	0,032
40	2,19	0,068	0,075	0,039
60	2,21	0,072	0,079	0,040

temperatures (< 90 °C), the recovery degree is low, and at higher temperatures, intensive evaporation and boiling of the productive solution occurs. During the leaching process, the ratio S:L ratio = 1:3 was taken, since this ratio is optimal.

At the end of each leaching experiment, the residue was filtered, rinsed with deionized water and dried in an electric oven at 70 °C. The experiments were repeated three times to obtain reproducible results with an accuracy of 0.5 %.

### Results and Discussion

From the data of mineralogical and X-ray spectral analysis of black shale ore, it follows that all valuable components are in a silicon-carbon matrix, which does not allow to completely extract valuable metals from ores. For processing of this raw material, it is necessary to have the technology allowing extraction most fully valuable metals into a productive solution.

At the next stage of the study, it was conducted a leaching of sintering products with a sulphate solution at different concentrations of sulfuric acid: temperature — 90 °C, S: L = 1:3, leaching time is 2 hours. The results of the investigation are presented in the table 3.

From the obtained data it follows that with an increase in the concentration of sulfuric acid to 40 g/L, the leaching rate of uranium, vanadium, molybdenum and rare earth metals increases significantly. The degree of extraction of vanadium, uranium, molybdenum and rare-earth elements is 81.7 %, 93.3 %, 82.2 %, and 78.3 %, respectively.

Research conducted by leaching sintering products at different duration of contact time with the solution. The process was conducted at the temperature of 80 °C, S: L = 1:3, the concentration of sulfuric acid is 40 g/L. The optimal leaching time is 2 hours was established in the previously published article [1].

### Conclusions

During sintering of ore with ammonium hydrosulfate, as a result of chemical reactions, water and the carbon contained in the black shale ore is in the form of dioxide are removed. Moreover, in this process vanadium, uranium, rare-earth sulfates and molybdenum oxide are formed.

By optimizing the technological modes, it was found that with low-temperature sintering of ore raw materials with ammonium hydrosulfate within 350 °C, further leaching with a solution of sulfuric acid at a temperature of 80 °C, extraction of uranium, vanadium, molybdenum and rare-earth metals reaches 98.2 %, 91.3 %, 82.2 % and 78.3 % respectively.

**Conflicts of interest.** On behalf of all authors, the corresponding author states that there is no conflict of interest.

**Acknowledgements.** The authors would like to thank A.Yu. Kuznetsov for providing ore materials and for the cooperation this research works. This work was financially supported by the MES RK (Ministry of Education and Science Republic of Kazakhstan).

*Cite this article as:* Khabiyev A. T., Baigenzhenov O. S., Yulussov S. B., Akbarov M. S., Sydykanov M. M. Study of leaching processes of sintered black shale ore. *Комплексное Использование Минерального Сырья*. = Complex Use of Mineral Resources = *Mineraldik Shikisattardy Keshendi Paidalanu*. - 2020. № 4 (315), pp. 5-10. <https://doi.org/10.31643/2020/6445.31>

### Литература

- [1] Baigenzhenov O.S., Yulussov S.B., Khabiyev A.T., Sydykanov M.M., Akbarov M.S. Investigation of the leaching process of rare-earth metals from the black shale ores of Greater Karatau. // *Complex Use of Mineral Resources*. 2019. №3 (310). Page: 76–80. <https://doi.org/10.31643/2019/6445.31>



- [2] Хабиев А.Т., Байгенженов О.С., Акбаров М.С., Сыдыканов М.М. Исследование возможности извлечения молибдена из сульфатных растворов на анионите Леватит MP62W5 // Комплексное использование минерального сырья (Complex Use of Mineral Resources). – 2020. – №2 (313). – С. 46-51. <https://doi.org/10.31643/2020/6445.16>
- [3] House, J. E. The development of the LIX reagents // Minerals and Metallurgical Processing. – 1989. – № 6 (1). – p. 1-6.
- [4] Coveney R.M, Watney W.L., Maples C.G., Contrasting depositional models for Pennsylvanian black shale discerned from molybdenum abundances // Geology. –1991. –19. P.147–150. [https://doi.org/10.1130/0091-7613\(1991\)019<0147:cdmfpb>2.3.co;2](https://doi.org/10.1130/0091-7613(1991)019<0147:cdmfpb>2.3.co;2)
- [5] Anjum F., Shahid M., Akcil A., Biohydrometallurgy techniques of low grade ores: A review on black shale // Hydrometallurgy. –2012. –117–118. P. 1-12. <https://doi.org/10.1016/j.hydromet.2012.01.007>
- [6] Kenzhaliyev B. K., Surkova T. YU., Yessimova D. M. Concentration of rare-earth elements by sorption from sulphate solutions // Complex Use of Mineral Resources –2019. –№3. – P. 5-9. <https://doi.org/10.31643/2019/6445.22>
- [7] Кенжалиев Б.К., Суркова Т.Ю., Юлусов С.Б., Пирматов Э.А., Дуленин А.П. Получение концентрата редкоземельных элементов из отходов и промпродуктов урановой промышленности // Комплексное использование минерального сырья. – 2017. – .№1. – С.70 –77. [www.kims-imio.kz](http://www.kims-imio.kz)

### Reference

- [1] Baigenzhenov O.S., Yulusov S.B., Khabiyev A.T., Sydykanov M.M., Akbarov M.S. Investigation of the leaching process of rare-earth metals from the black shale ores of Greater Karatau. // *Kompleksnoe Ispol'zovanie Mineral'nogo Syr'a = Complex Use of Mineral Resources*. 2019. №3 (310). Page: 76–80. (In English). <https://doi.org/10.31643/2019/6445.31>
- [2] Khabiyev A.T., Baigenzhenov O.S., Akbarov M.S., Sydykanov M.M. Issledovaniye vozmozhnosti izvlecheniya molibdena iz sul'fatnykh rastvorov na anionite Levatit MP62W5 [Study of the possibility of molybdenum recovery from sulfate solutions on the anionite Lewatit MP62W5] // *Kompleksnoe Ispol'zovanie Mineral'nogo Syr'a = Complex Use of Mineral Resources*. 2020. – №2 (313). – p.46-51. (In Russian). <https://doi.org/10.31643/2020/6445.16>
- [3] House, J. E. The development of the LIX reagents // Minerals and Metallurgical Processing. – 1989. – № 6 (1). – p. 1-6.
- [4] Coveney R.M, Watney W.L., Maples C.G., Contrasting depositional models for Pennsylvanian black shale discerned from molybdenum abundances // *Geology*. –1991.–19. P.147–150. (In English). [https://doi.org/10.1130/0091-7613\(1991\)019<0147:cdmfpb>2.3.co;2](https://doi.org/10.1130/0091-7613(1991)019<0147:cdmfpb>2.3.co;2)
- [5] Anjum F., Shahid M., Akcil A., Biohydrometallurgy techniques of low grade ores: A review on black shale // *Hydrometallurgy*. –2012. –117–118. P. 1-12. (In English). <https://doi.org/10.1016/j.hydromet.2012.01.007>
- [6] Kenzhaliyev B. K., Surkova T. YU., Yessimova D. M. Concentration of rare-earth elements by sorption from sulphate solutions // *Kompleksnoe Ispol'zovanie Mineral'nogo Syr'a = Complex Use of Mineral Resources*. 2019. –№3. – P. 5-9. (In English). <https://doi.org/10.31643/2019/6445.22>
- [7] Kenzhaliyev B. K., Surkova T. Yu., Yulusov S. B., Pirmatov E. A., Dulenin A. P. Polucheniye kontsentrata redkozemel'nykh elementov iz otkhodov i promproduktov uranovoy promyshlennosti [Obtaining a concentrate of rare earth elements from waste and industrial products of the uranium industry] // *Kompleksnoe Ispol'zovanie Mineral'nogo Syr'a = Complex Use of Mineral Resources*. 2017. – .№1. – С.70 –77. (In Russian). [www.kims-imio.kz](http://www.kims-imio.kz)